


**Poly[[( $\mu_2$ -benzene-1,4-dicarboxylato- $\kappa^4 O^1, O^{1'}:O^4, O^{4'}$ )( $\mu_2$ -di-4-pyridylidiazene- $\kappa^2 N^1:N^{1'}$ )cobalt(II)]  
 $N,N$ -dimethylformamide disolvate hemihydrate]**

**Chao-Xia Chu, Ying Zhang, Hu Zhou and Ai-Hua Yuan**

*Acta Cryst.* (2009). **E65**, m1035–m1036

This open-access article is distributed under the terms of the Creative Commons Attribution Licence <http://creativecommons.org/licenses/by/2.0/uk/legalcode>, which permits unrestricted use, distribution, and reproduction in any medium, provided the original authors and source are cited.



*Acta Crystallographica Section E: Structure Reports Online* is the IUCr's highly popular open-access structural journal. It provides a simple and easily accessible publication mechanism for the growing number of inorganic, metal-organic and organic crystal structure determinations. The electronic submission, validation, refereeing and publication facilities of the journal ensure very rapid and high-quality publication, whilst key indicators and validation reports provide measures of structural reliability. In 2007, the journal published over 5000 structures. The average publication time is less than one month.

**Crystallography Journals Online** is available from [journals.iucr.org](http://journals.iucr.org)

**Poly[[( $\mu_2$ -benzene-1,4-dicarboxylato- $\kappa^4O^1,O^{1'}:O^4,O^{4'}$ )( $\mu_2$ -di-4-pyridylidiazene- $\kappa^2N^1:N^{1'}$ )cobalt(II)]  $N,N$ -dimethyl-formamide disolvate hemihydrate]**

Chao-Xia Chu, Ying Zhang, Hu Zhou and Ai-Hua Yuan\*

School of Material Science and Engineering, Jiangsu University of Science and Technology, Zhenjiang 212003, People's Republic of China  
Correspondence e-mail: aihuayuan@163.com


Received 5 July 2009; accepted 29 July 2009

Key indicators: single-crystal X-ray study;  $T = 291$  K; mean  $\sigma(C-C) = 0.006$  Å; disorder in solvent or counterion;  $R$  factor = 0.057; wR factor = 0.134; data-to-parameter ratio = 16.4.

In the title compound,  $\{[Co(C_8H_4O_4)(C_{10}H_8N_4)] \cdot 2C_3H_7NO \cdot 0.5H_2O\}_n$ , the Co<sup>II</sup> atom is six-coordinated by four O atoms from two benzene-1,4-dicarboxylate ( $H_2bdc^{2-}$ ) groups and two N atoms from two 4,4'-azopyridine (4,4'-azpy, or di-4-pyridylidiazene) ligands, leading to a distorted octahedral geometry. The structure consists of two-dimensional corrugated sheets with a 4<sup>4</sup> topology in an ...ABAB... packing pattern stacking along the  $a$  axis. The separation of the adjacent corrugated sheets is ca. 8.561 (2) Å (Co···Co distance) along the  $a$  axis. The uncoordinated water molecule is half-occupied. The crystal structure is stabilized by O—H···N and C—H···O hydrogen-bonding interactions.

## Related literature

For background to metal-organic framework (MOF) materials, see: Halder & Kepert (2002); Murray & Cashion (2002); Rosi *et al.* (2003); Rowsell *et al.* (2005); Seo *et al.* (2000). For compounds containing H<sub>2</sub>bdc or 4,4'-azpy ligands, see: Halder *et al.* (2005); Jia (2007).

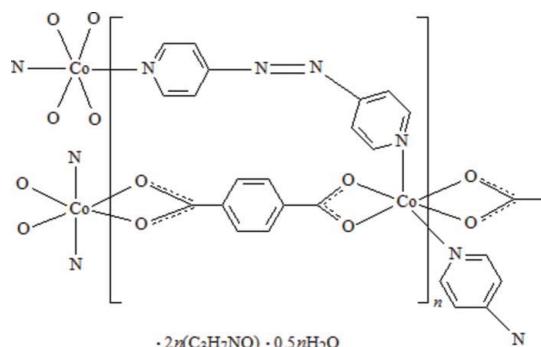

## Experimental

### Crystal data

$[Co(C_8H_4O_4)(C_{10}H_8N_4)] \cdot 2C_3H_7NO \cdot 0.5H_2O$	$V = 11293 (2)$ Å <sup>3</sup>
$M_r = 562.45$	$Z = 16$
Orthorhombic, $Fdd2$	Mo $K\alpha$ radiation
$a = 32.441 (4)$ Å	$\mu = 0.66$ mm <sup>-1</sup>
$b = 34.138 (4)$ Å	$T = 291$ K
$c = 10.1972 (12)$ Å	$0.25 \times 0.20 \times 0.08$ mm

### Data collection

Bruker SMART APEX CCD diffractometer	21948 measured reflections
Absorption correction: multi-scan ( <i>SADABS</i> ; Bruker, 2004)	5500 independent reflections
$T_{\min} = 0.84$ , $T_{\max} = 0.88$	4262 reflections with $I > 2\sigma(I)$
(expected range = 0.906–0.949)	$R_{\text{int}} = 0.062$

### Refinement

$R[F^2 > 2\sigma(F^2)] = 0.057$	H-atom parameters constrained
$wR(F^2) = 0.134$	$\Delta\rho_{\max} = 0.35$ e Å <sup>-3</sup>
$S = 1.07$	$\Delta\rho_{\min} = -0.36$ e Å <sup>-3</sup>
5500 reflections	Absolute structure: Flack (1983),
335 parameters	2564 Friedel pairs
1 restraint	Flack parameter: 0.04 (2)

**Table 1**  
Selected geometric parameters (Å, °).

N1—Co1	2.079 (4)	O2—Co1	2.153 (3)
N4—Co1 <sup>i</sup>	2.062 (4)	O3—Co1 <sup>iv</sup>	2.059 (3)
O1—Co1	2.153 (3)	O4—Co1 <sup>iv</sup>	2.353 (3)
Symmetry codes: (i) $x, y, z - 1$ ; (ii) $-x + \frac{3}{4}, y - \frac{1}{4}, z + \frac{1}{4}$ ; (iii) $x, y, z + 1$ ; (iv) $-x + \frac{3}{4}, y + \frac{1}{4}, z - \frac{1}{4}$ .			

**Table 2**  
Hydrogen-bond geometry (Å, °).

$D \cdots H$	$D—H$	$H \cdots A$	$D \cdots A$	$D—H \cdots A$
O7—H7A···N5 <sup>ii</sup>	0.85	2.32	2.932 (7)	129
C7—H7···O7	0.93	2.30	3.126 (7)	147
C16—H16···O3	0.93	2.48	2.791 (4)	100
C17—H17···O1	0.93	2.49	2.800 (4)	100
C19—H19C···O1 <sup>iv</sup>	0.96	2.37	3.150 (6)	138
C23—H23A···O6 <sup>v</sup>	0.96	1.71	2.624 (5)	158
Symmetry codes: (ii) $-x + \frac{3}{4}, y - \frac{1}{4}, z + \frac{1}{4}$ ; (iv) $-x + \frac{3}{4}, y + \frac{1}{4}, z - \frac{1}{4}$ ; (v) $-x + 1, -y + \frac{1}{2}, z + \frac{1}{2}$ .				

Data collection: *SMART* (Bruker, 2004); cell refinement: *SAINT* (Bruker, 2004); data reduction: *SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008) and *DIAMOND* (Brandenburg, 2006); software used to prepare material for publication: *SHELXL97*.

The work was supported by the University Natural Science Foundation of Jiangsu Province (No. 07KJB150030).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: AT2838).

# metal-organic compounds

---

## References

- Brandenburg, K. (2006). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Bruker (2004). *SMART* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Flack, H. D. (1983). *Acta Cryst. A* **39**, 876–881.
- Halder, G. J. & Kepert, C. J. (2005). *Aust. J. Chem.* **58**, 311–314.
- Halder, G. J., Kepert, C. J., Moubaraki, B., Murray, K. S. & Cashion, J. D. (2002). *Science*, **298**, 1762–1765.
- Jia, C.-X. (2007). *Acta Cryst. E* **63**, m615–m616.
- Murray, K. S. & Cashion, J. D. (2002). *Science*, **298**, 1762–1765.
- Rosi, N. L., Eckert, J., Eddaoudi, M., Vodak, D. T., Kim, J., O'Keeffe, M. & Yaghi, O. M. (2003). *Science*, **300**, 1127–1129.
- Rowsell, J. L. C., Spencer, E. C., Eckert, J., Howard, J. A. K. & Yaghi, O. M. (2005). *Science*, **309**, 1350–1354.
- Seo, J. S., Whang, D., Lee, H., Jun, S. I., Oh, J., Jeon, Y. J. & Kim, K. (2000). *Nature* (London), **404**, 982–986.
- Sheldrick, G. M. (2008). *Acta Cryst. A* **64**, 112–122.

## **supplementary materials**

*Acta Cryst.* (2009). E65, m1035-m1036 [doi:10.1107/S1600536809030189]

**Poly[[( $\mu_2$ -benzene-1,4-dicarboxylato- $\kappa^4$ O<sup>1</sup>,O<sup>1'</sup>:O<sup>4</sup>,O<sup>4'</sup>)( $\mu_2$ -di-4-pyridylidiazene- $\kappa^2$ N<sup>1</sup>:N<sup>1'</sup>)cobalt(II)] N,N-dimethylformamide disolvate hemihydrate]**

**C.-X. Chu, Y. Zhang, H. Zhou and A.-H. Yuan**

**Comment**

Metal organic framework (MOF) materials have attracted much attention due to their potential functionalities such as gas storage (Rosi *et al.*, 2003; Rowsell *et al.*, 2005), sensing (Halder *et al.*, 2002), and catalysis (Seo *et al.*, 2000). The organic ligands, especially, benzene-1,4-dicarboxylate ( $H_2bdc$ ) and 4,4'-azopyridine (4,4'-azpy), play a great role on constructing the topological architectures of MOFs (Jia, 2007; Halder *et al.*, 2005). Here we employed  $H_2bdc$  and 4,4'-azpy as mixed ligands to bridge the Co<sup>II</sup> atom, obtaining the title compound by solvothermal synthesis.

In the structure of the title compound, each Co<sup>II</sup> atom, lying on an inversion center, is coordinated by four oxygen atoms from two  $H_2BDC$  groups and two nitrogen atoms from two 4,4'-azpy ligands, exhibiting a slightly distorted octahedral geometry (Fig. 1). The bond lengths of Co—O range from 2.059 (3) to 2.353 (3) Å, while the ones of Co—N are 2.079 (4) Å for Co1—N1 and 2.062 (4) Å for Co1—N4, respectively (Table 1). The Co<sup>II</sup> centers are linked by  $H_2bdc$  groups into one-dimensional infinite zigzag chains along the *b* axis in the *bc* plane. Then, the chains are further linked by 4,4'-azpy ligands along the *c* axis, resulting in two-dimensional corrugated sheets with 4<sup>4</sup> topology. These corrugated sheets without interpenetration are stacking along the *a* axis in an ABAB packing mode (Fig. 2). The torsion angle of the adjacent sheets is *ca.* 45 ° in the *bc* plane, while the separation between adjacent corrugated sheets is *ca.* 8.56 Å (Co···Co distance) along the *a* axis.

The crystal structure is stabilized by O—H···N and C—H···O hydrogen bonding interactions (Table 2).

**Experimental**

A mixture of  $CoCl_2 \cdot 6H_2O$  (23.8 mg, 0.1 mmol),  $H_2bdc$  (16.6 mg, 0.1 mmol), 4,4'-azpy (18.4 mg, 0.1 mmol) and DMF (*N,N*-dimethylformamide) (10 ml) was stirred for 15 min at room temperature and then transferred into a Teflon-lined stainless-steel vessel. The mixture was heated at 433 K for two days under autogenous pressure. After cooling the resulting solution to room temperature with the rate of 10 °C/h, purple and layer-shaped crystals were obtained. Analysis calculated for  $Co_2N_{12}O_{13}C_{48}H_{54}$ : C 51.25, H 4.80, N 14.93%; found: C 51.16, H 4.65, N 14.92%.

**Refinement**

The C(H) atoms of the  $H_2bdc$  ligands, 4,4'-azpy ligands, and solvent DMF molecules were all placed in calculated position [ $C—H = 0.93$  Å or  $0.96$  Å] and refined using a riding model, with  $U_{iso}(H) = 1.2U_{eq}(C)$  or  $U_{iso}(H) = 1.5U_{eq}(C)$ . The O(H) atoms of the water molecules were located in a difference Fourier map and refined as riding [ $O—H = 0.85$  Å], with  $U_{iso}(H) = 1.2U_{eq}(O)$ .

# supplementary materials

---

## Figures

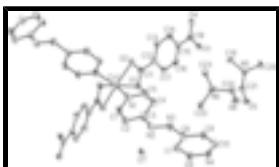


Fig. 1. ORTEP diagram of the title compound. Displacement ellipsoids are drawn at the 30% probability level. Hydrogen atoms are omitted for clarity.

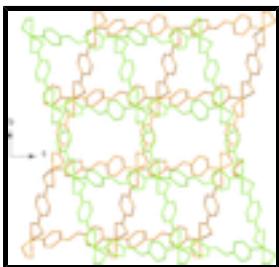


Fig. 2. View of the stacking without interpenetration of sheets along the  $a$  axis. Hydrogen atoms, solvent DMF molecules and water molecules are not involved for clarity.

## Poly[[ $\mu_2$ -benzene-1,4-dicarboxylato- $\kappa^4O^1,O^{1\prime}:O^4,O^{4\prime}$ )( $\mu_2$ -di-4-pyridylidiazene- $\kappa^2N^1:N^{1\prime}$ )cobalt(II)] $N,N$ -dimethylformamide disolvate hemihydrate]

### Crystal data

[Co(C <sub>8</sub> H <sub>4</sub> O <sub>4</sub> )(C <sub>10</sub> H <sub>8</sub> N <sub>4</sub> )·2C <sub>3</sub> H <sub>7</sub> NO·0.5H <sub>2</sub> O	$F_{000} = 4672$
$M_r = 562.45$	$D_x = 1.323 \text{ Mg m}^{-3}$
Orthorhombic, $Fdd2$	Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$
Hall symbol: F 2 -2d	Cell parameters from 3875 reflections
$a = 32.441 (4) \text{ \AA}$	$\theta = 2.2\text{--}24.4^\circ$
$b = 34.138 (4) \text{ \AA}$	$\mu = 0.66 \text{ mm}^{-1}$
$c = 10.1972 (12) \text{ \AA}$	$T = 291 \text{ K}$
$V = 11293 (2) \text{ \AA}^3$	Pale, purple
$Z = 16$	$0.25 \times 0.20 \times 0.08 \text{ mm}$

### Data collection

Bruker SMART APEX CCD diffractometer	5500 independent reflections
Radiation source: sealed tube	4262 reflections with $I > 2\sigma(I)$
Monochromator: graphite	$R_{\text{int}} = 0.062$
$T = 291 \text{ K}$	$\theta_{\text{max}} = 26.0^\circ$
$\varphi$ and $\omega$ scans	$\theta_{\text{min}} = 1.7^\circ$
Absorption correction: multi-scan (SADABS; Bruker, 2004)	$h = -40 \rightarrow 40$
$T_{\text{min}} = 0.84$ , $T_{\text{max}} = 0.88$	$k = -42 \rightarrow 41$
21948 measured reflections	$l = -12 \rightarrow 12$

### Refinement

Refinement on $F^2$	Hydrogen site location: inferred from neighbouring sites
---------------------	--

Least-squares matrix: full	H-atom parameters constrained
$R[F^2 > 2\sigma(F^2)] = 0.057$	$w = 1/[\sigma^2(F_o^2) + (0.07P)^2 + 1.99P]$
$wR(F^2) = 0.134$	where $P = (F_o^2 + 2F_c^2)/3$
$S = 1.07$	$(\Delta/\sigma)_{\max} < 0.001$
5500 reflections	$\Delta\rho_{\max} = 0.35 \text{ e \AA}^{-3}$
335 parameters	$\Delta\rho_{\min} = -0.36 \text{ e \AA}^{-3}$
1 restraint	Extinction correction: none
Primary atom site location: structure-invariant direct methods	Absolute structure: Flack (1983), 2564 Freidel pairs
Secondary atom site location: difference Fourier map	Flack parameter: 0.04 (2)

### Special details

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) etc. and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

### Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )

	$x$	$y$	$z$	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
C1	0.52950 (14)	0.07179 (14)	0.9140 (5)	0.0483 (11)	
H1	0.5231	0.0517	0.9724	0.058*	
C2	0.55879 (14)	0.06426 (13)	0.8190 (5)	0.0469 (10)	
H2	0.5719	0.0401	0.8153	0.056*	
C3	0.56831 (13)	0.09346 (13)	0.7291 (5)	0.0440 (10)	
C4	0.54745 (14)	0.12918 (13)	0.7419 (5)	0.0460 (11)	
H4	0.5529	0.1498	0.6847	0.055*	
C5	0.51897 (13)	0.13334 (13)	0.8397 (6)	0.0543 (12)	
H5	0.5050	0.1571	0.8452	0.065*	
C6	0.51064 (14)	0.08224 (13)	0.3277 (5)	0.0471 (10)	
H6	0.4900	0.0634	0.3279	0.057*	
C7	0.53796 (13)	0.08165 (13)	0.4260 (5)	0.0447 (11)	
H7	0.5355	0.0632	0.4927	0.054*	
C8	0.57026 (13)	0.10881 (12)	0.4282 (4)	0.0393 (10)	
C9	0.57199 (12)	0.13488 (13)	0.3217 (5)	0.0447 (10)	
H9	0.5932	0.1531	0.3151	0.054*	
C10	0.54305 (13)	0.13299 (13)	0.2316 (4)	0.0448 (10)	
H10	0.5449	0.1507	0.1625	0.054*	
C11	0.43039 (14)	0.16957 (14)	1.0169 (4)	0.0438 (10)	
C12	0.40496 (7)	0.20614 (7)	0.9897 (3)	0.0409 (10)	
C13	0.41490 (7)	0.24214 (8)	1.0450 (3)	0.0467 (11)	

## supplementary materials

---

H13	0.4377	0.2444	1.0996	0.056*
C14	0.39070 (9)	0.27481 (6)	1.0187 (3)	0.0460 (11)
H14	0.3973	0.2989	1.0557	0.055*
C15	0.35657 (8)	0.27148 (7)	0.9370 (3)	0.0463 (11)
C16	0.34663 (7)	0.23548 (8)	0.8817 (3)	0.0437 (10)
H16	0.3238	0.2333	0.8271	0.052*
C17	0.37083 (8)	0.20281 (6)	0.9081 (3)	0.0419 (10)
H17	0.3642	0.1787	0.8711	0.050*
C18	0.32954 (13)	0.30541 (13)	0.9112 (4)	0.0416 (10)
C19	0.34469 (15)	0.31385 (14)	0.5392 (4)	0.0459 (11)
H19A	0.3659	0.2965	0.5700	0.069*
H19B	0.3189	0.3068	0.5790	0.069*
H19C	0.3516	0.3403	0.5623	0.069*
C20	0.32794 (13)	0.34669 (13)	0.3270 (5)	0.0469 (11)
H20A	0.3427	0.3492	0.2459	0.070*
H20B	0.3336	0.3689	0.3818	0.070*
H20C	0.2989	0.3454	0.3094	0.070*
C21	0.35209 (14)	0.27414 (13)	0.3303 (5)	0.0465 (10)
H21A	0.3777	0.2632	0.3487	0.056*
C22	0.46065 (14)	0.18349 (13)	0.4854 (5)	0.0464 (11)
H22A	0.4494	0.1745	0.4037	0.070*
H22B	0.4432	0.1753	0.5561	0.070*
H22C	0.4877	0.1726	0.4971	0.070*
C23	0.44909 (13)	0.24827 (14)	0.6023 (4)	0.0464 (11)
H23A	0.4725	0.2557	0.6543	0.070*
H23B	0.4313	0.2317	0.6531	0.070*
H23C	0.4343	0.2713	0.5757	0.070*
C24	0.47026 (13)	0.24724 (14)	0.3600 (4)	0.0453 (10)
H24A	0.4547	0.2687	0.3336	0.054*
N1	0.50968 (12)	0.10580 (11)	0.9280 (4)	0.0501 (10)
N2	0.59730 (11)	0.08629 (11)	0.6303 (4)	0.0464 (9)
N3	0.59939 (11)	0.11042 (11)	0.5299 (4)	0.0464 (9)
N4	0.51102 (12)	0.10792 (11)	0.2297 (4)	0.0477 (10)
N5	0.34115 (11)	0.31054 (11)	0.3948 (4)	0.0462 (9)
N6	0.46332 (12)	0.22667 (11)	0.4842 (4)	0.0485 (9)
O1	0.41954 (9)	0.13759 (9)	0.9692 (3)	0.0463 (7)
O2	0.46054 (10)	0.17289 (9)	1.0912 (3)	0.0490 (8)
Co1	0.467820 (19)	0.110280 (18)	1.08164 (6)	0.04633 (17)
O3	0.30051 (9)	0.30257 (8)	0.8275 (3)	0.0450 (7)
O4	0.33472 (10)	0.33757 (9)	0.9713 (3)	0.0470 (7)
O5	0.32930 (9)	0.25672 (9)	0.2523 (3)	0.0490 (8)
O6	0.49957 (10)	0.23314 (9)	0.2912 (3)	0.0495 (8)
O7	0.49198 (17)	0.02737 (16)	0.6249 (6)	0.0438 (15)
H7A	0.4779	0.0440	0.6677	0.053*
H7C	0.5147	0.0233	0.6643	0.053*
				0.50

*Atomic displacement parameters ( $\text{\AA}^2$ )*

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
C1	0.055 (3)	0.041 (2)	0.049 (3)	0.003 (2)	0.011 (2)	0.018 (2)
C2	0.052 (2)	0.045 (2)	0.044 (2)	0.0129 (19)	0.004 (2)	0.011 (2)
C3	0.038 (2)	0.045 (2)	0.049 (3)	0.0034 (19)	-0.0015 (19)	0.013 (2)
C4	0.046 (2)	0.034 (2)	0.058 (3)	-0.0052 (19)	0.008 (2)	0.011 (2)
C5	0.039 (2)	0.041 (2)	0.083 (3)	0.0057 (19)	0.018 (3)	0.023 (3)
C6	0.046 (2)	0.051 (3)	0.044 (2)	-0.0026 (19)	-0.014 (2)	0.013 (2)
C7	0.041 (2)	0.044 (3)	0.049 (3)	-0.0074 (19)	-0.0096 (19)	0.0190 (19)
C8	0.034 (2)	0.037 (2)	0.047 (2)	0.0005 (17)	0.0021 (17)	0.0160 (18)
C9	0.046 (2)	0.049 (2)	0.039 (2)	-0.0168 (19)	0.004 (2)	0.016 (2)
C10	0.045 (2)	0.046 (2)	0.043 (2)	-0.002 (2)	-0.001 (2)	0.014 (2)
C11	0.043 (2)	0.049 (3)	0.039 (2)	0.0040 (19)	0.007 (2)	0.0094 (19)
C12	0.036 (2)	0.041 (2)	0.046 (2)	-0.0004 (17)	0.0028 (19)	-0.0029 (19)
C13	0.048 (2)	0.041 (2)	0.051 (3)	0.0011 (19)	-0.019 (2)	-0.0003 (19)
C14	0.042 (2)	0.052 (3)	0.044 (2)	0.011 (2)	-0.0092 (19)	-0.011 (2)
C15	0.053 (3)	0.048 (3)	0.038 (2)	0.006 (2)	-0.015 (2)	0.008 (2)
C16	0.039 (2)	0.053 (3)	0.039 (2)	0.0139 (19)	-0.0165 (18)	-0.002 (2)
C17	0.033 (2)	0.045 (2)	0.048 (3)	0.0103 (18)	0.0037 (18)	0.0088 (19)
C18	0.042 (2)	0.035 (2)	0.048 (3)	-0.0035 (17)	-0.0090 (19)	-0.0017 (19)
C19	0.050 (2)	0.047 (3)	0.040 (2)	0.011 (2)	-0.0153 (19)	-0.0161 (19)
C20	0.048 (2)	0.045 (2)	0.048 (2)	0.0133 (18)	0.025 (2)	0.024 (2)
C21	0.050 (2)	0.048 (2)	0.041 (2)	-0.0162 (19)	0.022 (2)	-0.011 (2)
C22	0.048 (2)	0.045 (2)	0.046 (2)	-0.016 (2)	-0.019 (2)	0.018 (2)
C23	0.041 (2)	0.052 (3)	0.046 (3)	-0.0109 (19)	0.0137 (19)	0.016 (2)
C24	0.044 (2)	0.047 (2)	0.045 (2)	0.0162 (19)	0.0128 (19)	-0.0123 (19)
N1	0.045 (2)	0.047 (2)	0.058 (3)	0.0075 (18)	0.0063 (19)	0.0187 (19)
N2	0.042 (2)	0.042 (2)	0.056 (2)	0.0049 (16)	0.0049 (17)	0.0180 (17)
N3	0.046 (2)	0.049 (2)	0.0442 (19)	-0.0205 (17)	-0.0080 (16)	0.0169 (17)
N4	0.055 (2)	0.049 (2)	0.039 (2)	-0.0110 (18)	0.0065 (18)	0.0142 (17)
N5	0.050 (2)	0.044 (2)	0.045 (2)	-0.0143 (17)	0.0165 (17)	0.0115 (17)
N6	0.048 (2)	0.047 (2)	0.051 (2)	-0.0154 (17)	0.0111 (17)	-0.0098 (18)
O1	0.0475 (17)	0.0440 (18)	0.0475 (18)	0.0113 (13)	0.0030 (14)	0.0084 (15)
O2	0.0545 (19)	0.0475 (17)	0.0449 (17)	0.0085 (14)	-0.0040 (16)	0.0148 (16)
Co1	0.0466 (3)	0.0478 (3)	0.0446 (3)	-0.0004 (3)	-0.0022 (3)	0.0112 (3)
O3	0.0485 (16)	0.0416 (16)	0.0449 (16)	-0.0065 (13)	-0.0155 (15)	0.0075 (15)
O4	0.0540 (18)	0.0358 (16)	0.0512 (18)	-0.0083 (14)	0.0009 (15)	0.0047 (14)
O5	0.0458 (17)	0.0489 (19)	0.0522 (19)	0.0146 (13)	-0.0144 (14)	-0.0177 (15)
O6	0.0505 (17)	0.0525 (18)	0.0456 (18)	-0.0203 (15)	0.0137 (14)	-0.0169 (14)
O7	0.040 (3)	0.038 (3)	0.053 (4)	0.010 (2)	0.015 (3)	0.014 (3)

*Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )*

C1—N1	1.335 (6)	C18—O4	1.268 (5)
C1—C2	1.381 (6)	C18—O3	1.275 (5)
C1—H1	0.9300	C19—N5	1.482 (6)
C2—C3	1.389 (6)	C19—H19A	0.9600

## supplementary materials

---

C2—H2	0.9300	C19—H19B	0.9600
C3—N2	1.399 (6)	C19—H19C	0.9600
C3—C4	1.401 (6)	C20—N5	1.478 (5)
C4—C5	1.367 (7)	C20—H20A	0.9600
C4—H4	0.9300	C20—H20B	0.9600
C5—N1	1.336 (6)	C20—H20C	0.9600
C5—H5	0.9300	C21—O5	1.238 (5)
C6—N4	1.329 (6)	C21—N5	1.449 (6)
C6—C7	1.338 (6)	C21—H21A	0.9300
C6—H6	0.9300	C22—N6	1.477 (6)
C7—C8	1.399 (6)	C22—H22A	0.9600
C7—H7	0.9300	C22—H22B	0.9600
C8—N3	1.404 (6)	C22—H22C	0.9600
C8—C9	1.405 (6)	C23—N6	1.486 (6)
C9—C10	1.315 (6)	C23—H23A	0.9600
C9—H9	0.9300	C23—H23B	0.9600
C10—N4	1.346 (6)	C23—H23C	0.9600
C10—H10	0.9300	C24—O6	1.276 (5)
C11—O2	1.242 (6)	C24—N6	1.465 (6)
C11—O1	1.246 (6)	C24—H24A	0.9300
C11—C12	1.522 (5)	N1—Co1	2.079 (4)
C12—C13	1.3900	N2—N3	1.316 (5)
C12—C17	1.3900	N4—Co1 <sup>i</sup>	2.062 (4)
C13—C14	1.3900	O1—Co1	2.153 (3)
C13—H13	0.9300	O2—Co1	2.153 (3)
C14—C15	1.3900	Co1—O3 <sup>ii</sup>	2.059 (3)
C14—H14	0.9300	Co1—N4 <sup>iii</sup>	2.062 (4)
C15—C16	1.3900	Co1—O4 <sup>ii</sup>	2.353 (3)
C15—C18	1.477 (5)	O3—Co1 <sup>iv</sup>	2.059 (3)
C16—C17	1.3900	O4—Co1 <sup>iv</sup>	2.353 (3)
C16—H16	0.9300	O7—H7A	0.8499
C17—H17	0.9300	O7—H7C	0.8501
N1—C1—C2	124.6 (4)	H19A—C19—H19C	109.5
N1—C1—H1	117.7	H19B—C19—H19C	109.5
C2—C1—H1	117.7	N5—C20—H20A	109.5
C1—C2—C3	118.8 (4)	N5—C20—H20B	109.5
C1—C2—H2	120.6	H20A—C20—H20B	109.5
C3—C2—H2	120.6	N5—C20—H20C	109.5
C2—C3—N2	119.9 (4)	H20A—C20—H20C	109.5
C2—C3—C4	117.1 (4)	H20B—C20—H20C	109.5
N2—C3—C4	123.0 (4)	O5—C21—N5	123.8 (4)
C5—C4—C3	119.0 (4)	O5—C21—H21A	118.1
C5—C4—H4	120.5	N5—C21—H21A	118.1
C3—C4—H4	120.5	N6—C22—H22A	109.5
N1—C5—C4	124.8 (4)	N6—C22—H22B	109.5
N1—C5—H5	117.6	H22A—C22—H22B	109.5
C4—C5—H5	117.6	N6—C22—H22C	109.5

N4—C6—C7	124.5 (4)	H22A—C22—H22C	109.5
N4—C6—H6	117.7	H22B—C22—H22C	109.5
C7—C6—H6	117.7	N6—C23—H23A	109.5
C6—C7—C8	119.9 (4)	N6—C23—H23B	109.5
C6—C7—H7	120.1	H23A—C23—H23B	109.5
C8—C7—H7	120.1	N6—C23—H23C	109.5
C7—C8—N3	122.8 (4)	H23A—C23—H23C	109.5
C7—C8—C9	115.9 (4)	H23B—C23—H23C	109.5
N3—C8—C9	121.3 (4)	O6—C24—N6	114.1 (4)
C10—C9—C8	118.7 (4)	O6—C24—H24A	122.9
C10—C9—H9	120.6	N6—C24—H24A	122.9
C8—C9—H9	120.6	C1—N1—C5	115.6 (4)
C9—C10—N4	126.3 (4)	C1—N1—Co1	117.3 (3)
C9—C10—H10	116.9	C5—N1—Co1	127.1 (3)
N4—C10—H10	116.9	N3—N2—C3	119.0 (4)
O2—C11—O1	122.7 (4)	N2—N3—C8	121.1 (3)
O2—C11—C12	117.6 (4)	C6—N4—C10	114.6 (4)
O1—C11—C12	119.6 (4)	C6—N4—Co1 <sup>i</sup>	124.7 (3)
O2—C11—Co1	61.4 (2)	C10—N4—Co1 <sup>i</sup>	120.7 (3)
O1—C11—Co1	61.4 (2)	C21—N5—C20	125.1 (4)
C12—C11—Co1	174.3 (3)	C21—N5—C19	119.8 (4)
C13—C12—C17	120.0	C20—N5—C19	115.0 (4)
C13—C12—C11	121.7 (2)	C24—N6—C22	119.6 (4)
C17—C12—C11	118.3 (2)	C24—N6—C23	120.7 (3)
C12—C13—C14	120.0	C22—N6—C23	118.1 (4)
C12—C13—H13	120.0	C11—O1—Co1	88.0 (3)
C14—C13—H13	120.0	C11—O2—Co1	88.2 (3)
C15—C14—C13	120.0	O3 <sup>ii</sup> —Co1—N4 <sup>iii</sup>	100.02 (14)
C15—C14—H14	120.0	O3 <sup>ii</sup> —Co1—N1	95.89 (14)
C13—C14—H14	120.0	N4 <sup>iii</sup> —Co1—N1	96.03 (14)
C16—C15—C14	120.0	O3 <sup>ii</sup> —Co1—O2	156.86 (12)
C16—C15—C18	118.9 (2)	N4 <sup>iii</sup> —Co1—O2	94.61 (14)
C14—C15—C18	121.0 (2)	N1—Co1—O2	100.31 (14)
C17—C16—C15	120.0	O3 <sup>ii</sup> —Co1—O1	101.14 (13)
C17—C16—H16	120.0	N4 <sup>iii</sup> —Co1—O1	154.34 (15)
C15—C16—H16	120.0	N1—Co1—O1	96.06 (14)
C16—C17—C12	120.0	O2—Co1—O1	60.96 (12)
C16—C17—H17	120.0	O3 <sup>ii</sup> —Co1—O4 <sup>ii</sup>	59.18 (11)
C12—C17—H17	120.0	N4 <sup>iii</sup> —Co1—O4 <sup>ii</sup>	92.07 (13)
O4—C18—O3	119.2 (4)	N1—Co1—O4 <sup>ii</sup>	154.85 (14)
O4—C18—C15	120.9 (4)	O2—Co1—O4 <sup>ii</sup>	102.73 (12)
O3—C18—C15	119.9 (3)	O1—Co1—O4 <sup>ii</sup>	86.45 (11)
N5—C19—H19A	109.5	C18—O3—Co1 <sup>iv</sup>	97.3 (2)
N5—C19—H19B	109.5	C18—O4—Co1 <sup>iv</sup>	84.1 (3)
H19A—C19—H19B	109.5	H7A—O7—H7C	109.5
N5—C19—H19C	109.5		

## supplementary materials

---


Symmetry codes: (i)  $x, y, z-1$ ; (ii)  $-x+3/4, y-1/4, z+1/4$ ; (iii)  $x, y, z+1$ ; (iv)  $-x+3/4, y+1/4, z-1/4$ .

*Hydrogen-bond geometry ( $\text{\AA}$ ,  $^\circ$ )*

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
O7—H7A $\cdots$ N5 <sup>ii</sup>	0.85	2.32	2.932 (7)	129
C7—H7 $\cdots$ O7	0.93	2.30	3.126 (7)	147
C16—H16 $\cdots$ O3	0.93	2.48	2.791 (4)	100
C17—H17 $\cdots$ O1	0.93	2.49	2.800 (4)	100
C19—H19C $\cdots$ O1 <sup>iv</sup>	0.96	2.37	3.150 (6)	138
C23—H23A $\cdots$ O6 <sup>v</sup>	0.96	1.71	2.624 (5)	158

Symmetry codes: (ii)  $-x+3/4, y-1/4, z+1/4$ ; (iv)  $-x+3/4, y+1/4, z-1/4$ ; (v)  $-x+1, -y+1/2, z+1/2$ .

Fig. 1

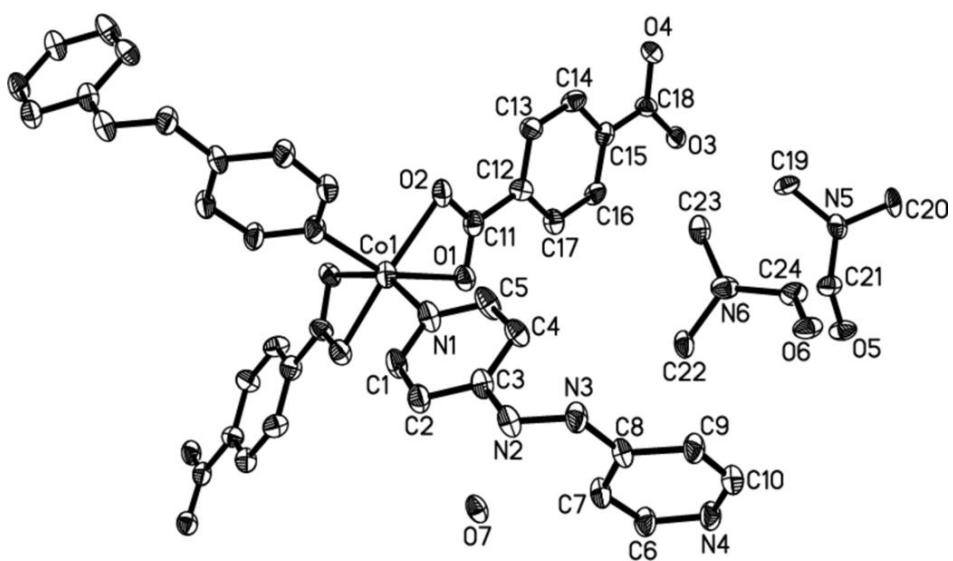

## **supplementary materials**

---

**Fig. 2**

