

This article was downloaded by: [Chulalongkorn University]
On: 26 December 2014, At: 20:35
Publisher: Taylor & Francis
Informa Ltd Registered in England and Wales Registered Number:
1072954 Registered office: Mortimer House, 37-41 Mortimer Street,
London W1T 3JH, UK


Journal of Coordination Chemistry

Publication details, including instructions for authors and subscription information:
<http://www.tandfonline.com/loi/gcoo20>

Synthesis, Crystal Structure and Magnetic Properties of a Two-Dimensional Heterometallic Assembly $I[Mn(salen)]I_2I[Ni(CN)_4] \cdot 1/2H_2O$

Ai-Hua Yuan ^a, Xiao-Ping Shen ^a, Qiang-Jin Wu ^a, Zi-Xiang Huang ^a & Zheng Xu ^a

^a Department of Materials and Environment Engineering, East China Shipbuilding Institute, Zhenjiang, 212003, P R China
Published online: 15 Sep 2010.

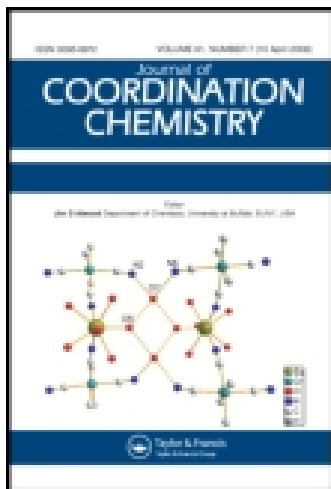

To cite this article: Ai-Hua Yuan, Xiao-Ping Shen, Qiang-Jin Wu, Zi-Xiang Huang & Zheng Xu (2010) Synthesis, Crystal Structure and Magnetic Properties of a Two-Dimensional Heterometallic Assembly $I[Mn(salen)]I_2I[Ni(CN)_4] \cdot 1/2H_2O$, Journal of Coordination Chemistry, 55:4, 411-420, DOI: [10.1080/00958970211905](https://doi.org/10.1080/00958970211905)

To link to this article: <http://dx.doi.org/10.1080/00958970211905>

PLEASE SCROLL DOWN FOR ARTICLE

Taylor & Francis makes every effort to ensure the accuracy of all the information (the "Content") contained in the publications on our platform. However, Taylor & Francis, our agents, and our licensors make no representations or warranties whatsoever as to

the accuracy, completeness, or suitability for any purpose of the Content. Any opinions and views expressed in this publication are the opinions and views of the authors, and are not the views of or endorsed by Taylor & Francis. The accuracy of the Content should not be relied upon and should be independently verified with primary sources of information. Taylor and Francis shall not be liable for any losses, actions, claims, proceedings, demands, costs, expenses, damages, and other liabilities whatsoever or howsoever caused arising directly or indirectly in connection with, in relation to or arising out of the use of the Content.

This article may be used for research, teaching, and private study purposes. Any substantial or systematic reproduction, redistribution, reselling, loan, sub-licensing, systematic supply, or distribution in any form to anyone is expressly forbidden. Terms & Conditions of access and use can be found at <http://www.tandfonline.com/page/terms-and-conditions>

**SYNTHESIS, CRYSTAL STRUCTURE
AND MAGNETIC PROPERTIES
OF A TWO-DIMENSIONAL
HETEROMETALLIC ASSEMBLY
[Mn(SALEN)]₂[Ni(CN)₄]·1/2H₂O**

AI-HUA YUAN^{a,*}, XIAO-PING SHEN^b, QIANG-JIN WU^c,
ZI-XIANG HUANG^c and ZHENG XU^d

^aDepartment of Materials and Environment Engineering, East China Shipbuilding Institute, Zhenjiang (212003), P R China; ^bDepartment of Chemistry, Zhenjiang Teacher's College, Zhenjiang (212003), P R China; ^cState Key Laboratory of Structural Chemistry, Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences, Fuzhou, Fujian (350002), P R China;

^dCoordination Chemistry Institute, State Key Laboratory of Coordination Chemistry, Nanjing University, Nanjing (210093), P R China

(Received 2 October 2000; In final form 22 March 2001)

A heterometallic assembly, [Mn(salen)]₂[Ni(CN)₄]·1/2H₂O (where salen = N, N'-ethylene-bis(salicylideneiminato)-dianion), has been prepared from the reaction of [Mn(salen)H₂O]·ClO₄·H₂O with K₂[Ni(CN)₄]·H₂O in methanol/water. The compound crystallizes in the tetragonal space group P 4/ncc with the cell dimensions of $a = 14.604(2)$ Å, $c = 16.949(3)$ Å, and $Z = 4$. The compound assumes a two-dimensional distorted square network structure, formed from Ni—CN—Mn(salen)—NC—Ni linkages with dimensions of Ni—C = 1.867(7) Å, Mn—N = 2.312(6) Å, Mn—N—C = 163.8(6)°, Ni—C—N = 178.4(6)°. The two metal atoms Ni(II) and Mn(III) have square and slightly distorted octahedral arrangements, respectively. Magnetic susceptibility measurements indicate the presence of an intramolecular antiferromagnetic interaction and gives a Mn—Mn exchange integral of -3.2 cm^{-1} .

Keywords: Nickel complex; Manganese complex; Cyano bridge; Crystal structure; Magnetic properties

*Corresponding author. e-mail: yah888@public.zj.js.cn

INTRODUCTION

The molecular design of extended structures starting from molecular precursors is an area of intense interest [1, 2]. The use of ionic building blocks, for example, in which one unit contains a potential bridging ligand and another contains a potential coordination site, can result in such molecular species. Extended bimetallic arrays assembled from hexacyano-metallate and metal ions bonded to polydentate ligands, have recently received particular attention [3–5]. These assemblies assume 1-D, 2-D and 3-D structures and exhibit ferro- or meta-magnetic behavior. For instance, the reaction between $[\text{Mn}(\text{BS})]^+$ [BS = salen-substituted ligand; salen = N, N'-ethylene-bis(salicylideneimino)-dianion] and $[\text{Fe}(\text{CN})_6]^{3-}$ led to a variety of extended structures depending on the nature of the Schiff base, the counteraction and the reaction solvent, *e.g.*, a 1-D chain complex $[\text{NEt}_4]_2 \{\text{Mn}(\text{acacen})\}[\text{Fe}(\text{CN})_6]$ [6], 2-D network complexes $\text{K}\{\text{Mn}(3\text{-MeOsalen})\}_2 [\text{Fe}(\text{CN})_6]$ [7] and $\{\{\text{Mn}(\text{saltmen})\}_4\{\text{Fe}(\text{CN})_6\}\}\text{ClO}_4 \cdot \text{H}_2\text{O}$ [7] have been synthesized and characterized in detail; these complexes invariably exhibit a ferromagnetic interaction between the adjacent manganese(III) and iron (III) ions through the cyano bridge. It has been found that the number of *d*-electrons in the central metal ions and the structure of the complex ions plays a very important role in the magnetic properties. To clarify the relationship between the number of *d*-electrons of central metal, the molecular structure and magnetic property of double complexes with the $[\text{Mn}(\text{salen})]^+$ cation, we have synthesized the title complex $[\text{Mn}(\text{salen})]_2 [\text{Ni}(\text{CN})_4] \cdot 1/2\text{H}_2\text{O}$ from $[\text{Mn}(\text{salen})\text{H}_2\text{O}]^+$ and $[\text{Ni}(\text{CN})_4]^{2-}$, and studied its structure and magnetic properties.

EXPERIMENTAL

Measurements

Elemental analyses for carbon, hydrogen and nitrogen were performed on a Perkin-Elmer 240C microanalysis instrument. Manganese and nickel analyses were made on a Jarrell-Ash 1100 + 2000 inductively coupled plasma quantometer. Infrared spectra were measured on KBr disks with a Nicolet FT-170SX spectrometer. Magnetic susceptibilities were measured with a MPMS-5 SQUID susceptometer under an applied magnetic field of 10000 Oe in the 5–299K temperature range. Diamagnetic corrections were made using Pascal's constants. Effective magnetic moments were calculated by the

equation $\mu_{\text{eff}} = 2.828(\chi_{\text{M}} \times T)^{1/2}$, where χ_{M} is the magnetic susceptibility per formula unit.

Preparation

General Procedures and Materials

All chemicals and solvents used for the synthesis were reagent grade. The quadridentate Schiff-base ligand SalenH₂ was prepared by mixing salicylaldehyde and ethylenediamine in a 2:1 molar ratio in methanol according to the literature [8, 9], [Mn(salen) H₂O] ClO₄·H₂O was prepared by mixing Mn(OAc)₃·2H₂O, SalenH₂ and NaClO₄ in a molar ratio of 1:1:1.5 in methanol according to the method reported previously [10].

Preparation of [Mn(Salen)]₂[Ni(CN)₄]·1/2H₂O

A solution of [Mn(salen)H₂O] ClO₄·H₂O (0.456 g, 1 mmol) in a mixture of methanol (30 mL) and DMF (5 mL) was added to a solution of K₂[Ni(CN)₄]·H₂O (0.13 g, 0.5 mmol) in water (10 mL) at room temperature. The resulting solution was filtered and the filtrate was kept a week in the dark. The resulting black pillar crystals were collected by filtration, washed with methanol and dried in air. Anal. Calcd for C₃₆H₂₉Mn₂Ni₈O_{4.5} (%): C, 53.10; H, 3.59; N, 13.76; Ni, 7.21; Mn, 13.49. Found: C, 52.43; H, 3.55; N, 13.32; Ni, 7.38; Mn, 13.60. IR (cm⁻¹): $\nu_{\text{C=N}}$ (imine):1600(s), 1634.6(v/s); $\nu_{\text{C}\equiv\text{N}}$ (cyanide): 2128.7(m).

X-ray Data Collection, Reduction and Structure Determination

A crystal of the title complex with dimensions of 0.575 × 0.25 × 0.225 mm was stuck to the end of a glass fiber and then mounted on an Enraf -Nonius CAD4 diffractometer to perform X-ray diffraction using graphite-mo-chromated Mo-K_α radiation ($\lambda = 0.71073 \text{ \AA}$). The unit cell parameters were determined and refined by a least-squares treatment of the setting angles of 25 automatically centered reflections ($12.94 < \theta < 13.89$). The intensity data were collected by using $\omega - 2\theta$ scan mode in the range of $2^\circ < \theta < 26^\circ$. There was no evidence of crystal decay from three standard reflections monitored every two hours throughout the data collection. The total 3365 reflections measured were corrected for Lp effects and the absorption using Ψ scan technique (T_{max} and T_{min} are 1.0000 and 0.9327, respectively), 1741 unique data were obtained, of which 1262 reflections with intensities $I \geq 2\sigma(I)$ were

TABLE I Crystallographic data for $[\text{Mn}(\text{Salen})]_2[\text{Ni}(\text{CN})_4] \cdot 1/2\text{H}_2\text{O}^*$

| | | | |
|-----------------|---|---------------------------------------|------------|
| Formula | $\text{C}_{36}\text{H}_{29}\text{Mn}_2\text{NiN}_8\text{O}_{4.5}$ | $V(\text{\AA}^3)$ | 3614.9(10) |
| Formula weight | 814.26 | z | 4 |
| Crystal system | Tetragonal | $D_c (\text{g} \cdot \text{cm}^{-3})$ | 1.496 |
| Space group | $P4/ncc$ | $\mu(\text{cm}^{-1})$ | 12.55 |
| $a(\text{\AA})$ | 14.604(2) | $F(000)$ | 1660 |
| $b(\text{\AA})$ | 14.604(2) | R_{int} | 0.0555 |
| $c(\text{\AA})$ | 16.949(3) | R_1 | 0.0748 |
| GOF | 1.138 | wR_2 | 0.1861 |

$$^* R_1 = \frac{\sum ||F_o| - |F_c||}{\sum |F_o|}, wR_2 = \frac{\sum w(F_o^2 - F_c^2)^2 / \sum [w(F_o^2)^2]^{1/2}}{\sum w(F_o^2)^2 + 14.8468P}^{-1}, \text{ where } P = (F_o^2 + 2F_c^2)/3 \text{ GOF} = \left[\frac{\sum w(|F_o| - |F_c|)^2}{(N_{\text{obs}} - N_{\text{param}})} \right]^{1/2}.$$

used in the structure solution and refinement. The structure was solved by direct methods and subsequent Fourier difference syntheses. All non-hydrogen atoms were refined with anisotropic thermal parameters. The idealized positions of the hydrogen atoms were located by using a riding model. The scattering contributions of the hydrogen atoms were added to the structure factor calculations but their positions were not refined. Full matrix least-squares refinement was based on F^2 . The number of refined parameters is 120. The final agreement factors were $R_1=0.0748$, $wR_2=0.1861$, $(\Delta/\sigma)_{\text{max}}$ on the final cycle was 0.00. The maximum and minimum residual densities on the final difference Fourier map were 0.682 and $-0.843 \text{ e}/\text{\AA}^3$, respectively. All the calculations were carried out on a microcomputer PIII-450 with the SHELXTL97 program [11]. A summary of the pertinent crystallographic data and the main results are listed in Table I.

RESULTS AND DISCUSSION

Crystal Structure

The ORTEP diagrams of the title complex with the atom numbering scheme is shown in Figure 1. The packing diagram projected along the c -axis and a -axis are given in Figures 2 and 3, respectively. The selected bond distances and angles are listed in Table II. The molecular structure consists of one $\text{Ni}(\text{CN})_4^{2-}$ anion, two $\text{Mn}(\text{Salen})^+$ cations and one crystal water molecule. The anion and cation are linked by $\text{Ni}-\text{CN}-\text{Mn}$ assemblies to form a two dimensional distorted square network packing structure in the $\{ab\}$ plane (see Fig. 2). The Ni atom is located on the four-fold axis and coordinated by four equivalent CN^- ligands with $\text{Ni}-\text{C}$ bond lengths of $1.867(7) \text{ \AA}$ and $\text{Ni}-\text{C}-\text{N}$ angles of $178.4(6)^\circ$. The Mn atom lies on the two-fold axis, which

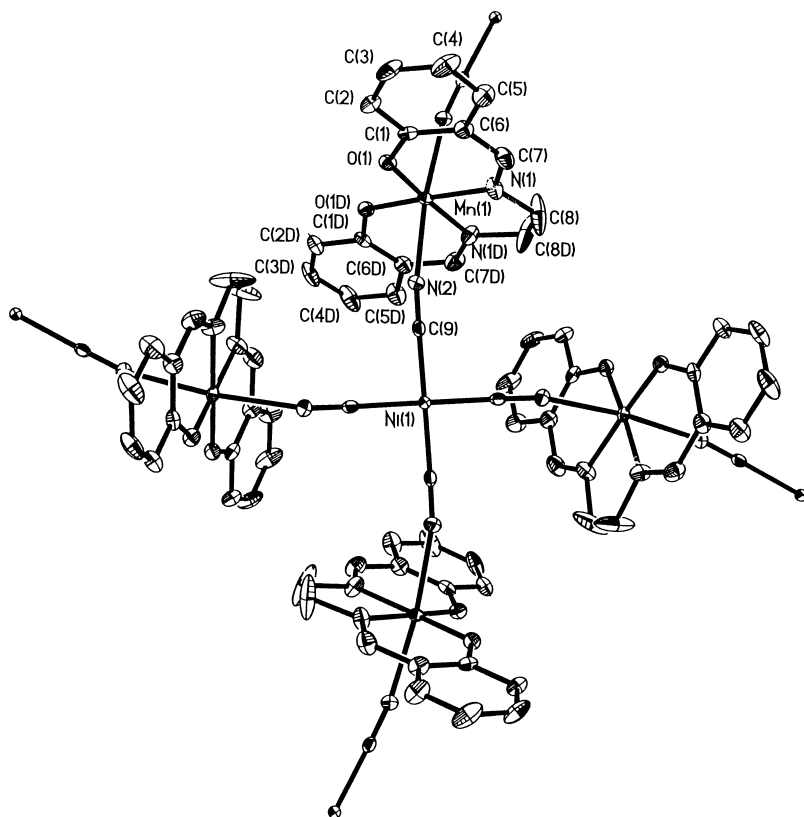


FIGURE 1 ORTEP drawing of the title complex with the atom-numbering scheme.

also crosses in the middle of $-\text{CH}_2-\text{CH}_2-$ bond. Two CN^- ligands coordinate to a Mn center by N atoms, thus constructing a slightly distorted octahedral coordination geometry for Mn in which the equatorial sites are occupied by N_2O_2 donor atoms of the quadridentate Schiff-base ligand salen and the two axial positions are occupied by two nitrogen atoms from CN^- groups. The Mn ion is bound by two equally strong π -bonding CN^- groups, which is different from those observed in the 2D $[\text{Mn}(\text{salen-substituted})]^+ / [\text{Fe}(\text{CN})_6]^{3-}$ adducts [7, 12]. The Mn–N(CN) distance of 2.312(6) Å and the Mn–N–C angle of 163.8(6)° are averages of those observed in above adducts. The Mn–Ni and Mn–Mn separations along the Ni–CN–Mn linkage are 5.278 and 10.556 Å, respectively. The bonding parameters of the salen ligand with Mn are similar to those found in related complexes reported previously.

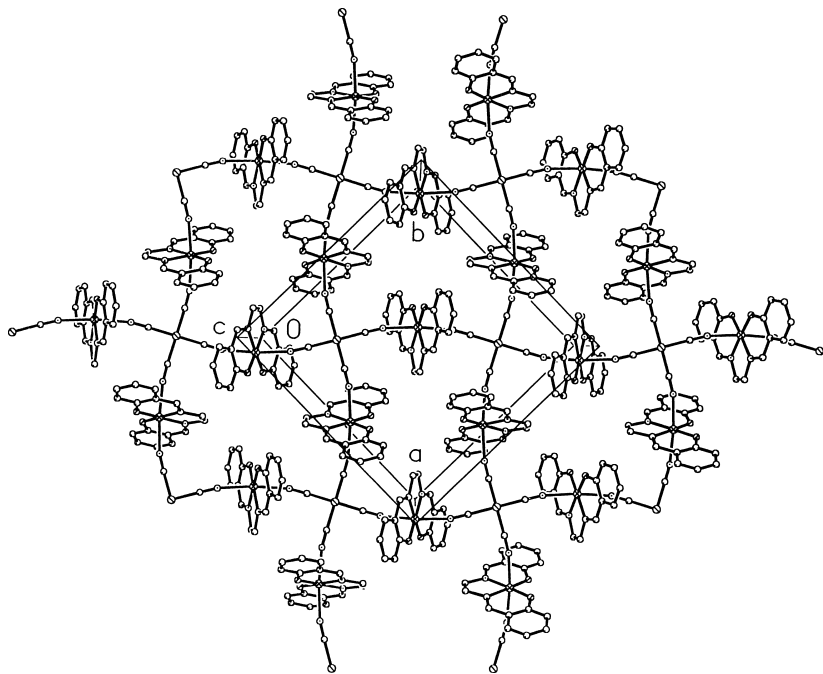


FIGURE 2 Projection along the *c*-axis for the title complex, showing a two-dimensional network structure.

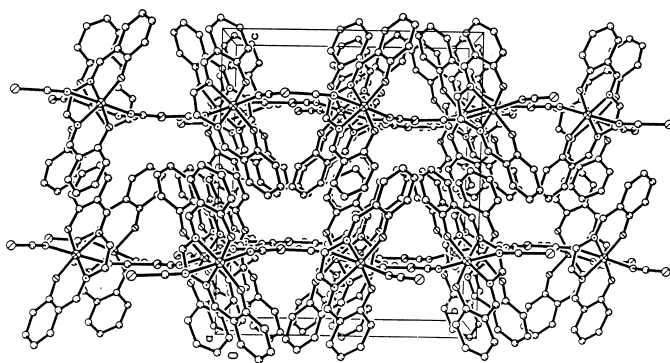


FIGURE 3 Projection along the *a*-axis for the title complex, showing a stacking of the layer structure.

As already mentioned, all the CN^- ligands bridge Ni and Mn centers to give a wave-like chain (see Figs. 2 and 3). The distance between two chains is 8.747 Å. The nearest intralayer and interlayer Mn—Mn separations through

TABLE II Selected bond lengths (Å) and angles (°) for the title complex, with the estimated standard deviations in parentheses

| | | | |
|--------------------------------|------------|--------------------------------|------------|
| Ni(1)—C(9) | 1.867 (7) | Mn(1)—N(2) | 2.312 (6) |
| Mn(1)—O(1) | 1.892 (5) | Mn(1)—N(1) | 1.983 (6) |
| O(1)—C(1) | 1.312 (8) | N(1)—C(7) | 1.263 (9) |
| N(1)—C(8) | 1.474 (11) | N(2)—C(9) | 1.158 (9) |
| C(1)—C(6) | 1.389 (11) | C(1)—C(2) | 1.406 (10) |
| C(2)—C(3) | 1.374 (11) | C(3)—C(4) | 1.359 (15) |
| C(4)—C(5) | 1.360 (13) | C(5)—C(6) | 1.402 (10) |
| C(6)—C(7) | 1.436 (11) | C(8)—C(8) ^{#3} | 1.277 (18) |
| C(9) ^{#1} —Ni(1)—C(9) | 89.986 (7) | C(9) ^{#2} —Ni(1)—C(9) | 178.2 (4) |
| O(1)—Mn(1)—O(1) ^{#3} | 96.2 (3) | O(1)—Mn(1)—N(1) ^{#3} | 172.3 (2) |
| O(1)—Mn(1)—N(1) | 91.2 (2) | O(1)—Mn(1)—N(2) | 93.9 (2) |
| N(1) ^{#3} —Mn(1)—N(1) | 81.5 (3) | O(1) ^{#3} —Mn(1)—N(2) | 90.2 (2) |
| N(1)—Mn(1)—N(2) | 91.4 (3) | N(1)—Mn(1)—N(2) ^{#3} | 84.0 (3) |
| N(2)—Mn(1)—N(2) ^{#3} | 174.0 (3) | C(1)—O(1)—Mn(1) | 128.1 (5) |
| C(7)—N(1)—Mn(1) | 126.3 (6) | C(8)—N(1)—Mn(1) | 112.7 (5) |
| C(9)—N(2)—Mn(1) | 163.8 (6) | N(2)—C(9)—Ni(1) | 178.4 (6) |

Symmetry transformations used to generate equivalent atoms:

^{#1} $-y + 1/2, x, z,$

^{#2} $-x + 1/2, -y + 1/2, z,$

^{#3} $y + 1/2, x - 1/2, -z + 1/2.$

space are 7.419 Å and 8.676 Å, respectively. The crystal water molecule fills the vacant position of the square net and can be regarded as a clathrated solvent molecule. No hydrogen bonds exist in this structure.

Magnetic Properties

The variable-temperature magnetic susceptibility was measured from 5 to 299K by a SQUID magnetometer under the applied magnetic field of 10000 Oe. Plots of the magnetic susceptibility (χ_M) and the effective magnetic moment (μ_{eff}) vs. temperature (T) are shown in Figure 4. The μ_{eff} per Mn_2Ni unit at 299K, $3.90 \mu_B$, is much smaller than the spin-only value of $6.93 \mu_B$ expected for the magnetically dilute high spin Mn(III) ions [$(S_{\text{Mn}}, S_{\text{Ni}}, S_{\text{Mn}}) = (2, 0, 2)$], but is nearly equal to the value of $4.0 \mu_B$ expected for the magnetically dilute low spin Mn(III) ions [$(S_{\text{Mn}}, S_{\text{Ni}}, S_{\text{Mn}}) = (1, 0, 1)$], where the spin-only values were calculated by assuming $g_{\text{Mn}} = 2.00$. This suggests that the complex contains low spin Mn(III) and is different from previously characterized Mn(III) analogues [6, 7, 12], which usually involve high spin Mn(III) ions. On lowering the temperature, μ_{eff} gradually decreases to $2.50 \mu_B$ at 23K, then reaches a plateau in the range of 238K, and finally decreases to $2.47 \mu_B$ at 5K, which suggests the presence of an antiferromagnetic exchange interaction. As $[\text{Ni}(\text{CN})_4]^{2-}$ is diamagnetic, the exchange interaction between Ni(II)—Mn(III) through the cyanide bridging ligand is negligible. However, the coupling between two adjacent

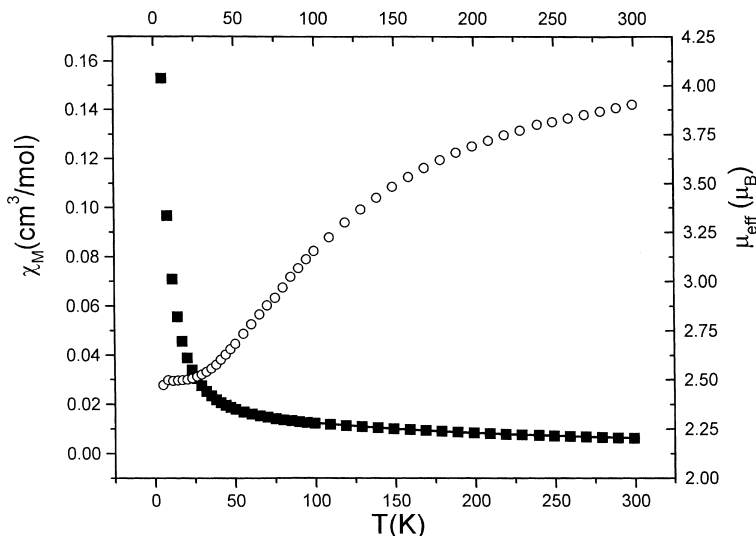


FIGURE 4 The temperature-dependence of magnetic susceptibility χ_M (■) and the effective magnetic moment μ_{eff} (○) for the title complex. The solid line represents the fit discussed in the text.

Mn(III) ions could occur through the $[\text{Ni}(\text{CN})_4]^{2-}$ group. The linear part of the $1/\chi_M$ vs. T curve ($T > 65$ K) was fitted to the Curie-Weiss law $\chi_M = C/(T - \theta)$ ($R = 0.9998$) with a big negative Weiss constant of $\theta = -107$ K, indicating the existence of a fairly big antiferromagnetic interaction between Mn(III) ions.

The susceptibility data were modeled in a similar way to that reported previously [13]. The susceptibility above 23 K can be approximated by Eqs. (1–4),

$$\chi_t = \frac{2Ng^2\beta^2}{3kT} \frac{15 \exp(6J/kT) + 3 \exp(2J/kT)}{5 \exp(6J/kT) + 3 \exp(2J/kT) + 1} \quad (1)$$

$$\chi_t = \frac{Ng^2\beta^2}{3kT} S_t(S_t + 1) \quad (2)$$

$$\chi_{\text{chain}} = \frac{Ng^2\beta^2}{3kT} \frac{1+u}{1-u} \times S_t(S_t + 1),$$

where $u = \coth[J_c S_t(S_t + 1)/kT] - kT/J_c S_t(S_t + 1)$ (3)

$$\chi_M = \frac{\chi_{\text{chain}}}{1 - \chi_{\text{chain}}(2zJ'/Ng^2\beta^2)}, \quad \text{where } z = 2 \quad (4)$$

where J_t , J_c and J' stand for the exchange integrals between two S_{Mn} ($S = 1$) spins within the Mn_2Ni trimer, between the S_t effective spins of trimers and between the chains, respectively, and were treated as equivalent. The symbols N , g , β and k have their usual meanings. When allowing the g and J values to vary, we obtained the best fit to the experimental data with parameters $J_t = J_c = J' = -3.2 \text{ cm}^{-1}$, $g = 1.98$ and the disagreement factor $R = 1.56 \times 10^{-3}$ [$R = \sum (\chi_{\text{obs}} - \chi_{\text{calc}})^2 / \chi_{\text{obs}}^2$]. As shown in Figure 5, the fit may be considered fairly good. The results ($J_t = J_c = J' < 0$) show the presence of an antiferromagnetic interaction between the Mn(III) ions within each sheet through the $-NC-Ni-CN-$ bridges. If one takes into consideration the electronic configurations of Mn(III) (t_{2g}^4) and $[Ni(CN)_4]^{2-}$, a π -superexchange pathway is proposed between the nearest Mn(III) ions through the Π_9^8 conjugation system of the $[Ni(CN)_4]^{2-}$ ion. The magnetic orbital d_{xz} (or d_{yz}) of Mn(III) may overlap with the Π_9^8 system (z axis is taken along the Mn—NC—Ni linkage), which transmits a magnetic interaction between adjacent Mn(III) ions and results in an antiferromagnetic interaction. Due to the symmetry, another magnetic orbital of Mn(III) cannot effectively overlap with the Π_9^8 system and there exists no coupling between these magnetic orbitals, which can perhaps account for the plateau in magnetic moment in 23–8 K with a value of $2.50 \mu_B$ that corresponds to about one unpaired electron per Mn center. The decrease in magnetic moment below 8 K may be due to an intersheet antiferromagnetic interaction or an antiferromagnetic coupling between the remaining magnetic orbitals of Mn(III) ions. Further study on the magnetic behavior is underway.

References

- [1] C. T. Chen and K. S. Suslick, *Coord. Chem. Rev.* **128**, 293 (1993).
- [2] D. Gatteschi, O. Kahn, J. S. Miller and F. Palacio, *Molecular Magnetic Materials*, The Netherlands, 1992, pp. 35–52.
- [3] M. Ohba, H. Okawa, T. Ito and A. Ohto, *J. Chem. Soc. Chem. Commun.* p. 1545 (1995).
- [4] E. Colacio, J. M. Dominguez-Vera, M. Ghazi, R. Kivekas, M. Klinga and J. M. Moreno, *J. Chem. Soc. Chem. Commun.* p. 1071 (1998).
- [5] S. Ferlay, T. Mallah, J. Vaissermann, F. Bartolome, P. Veillet and M. Verdager, *J. Chem. Soc. Chem. Commun.* p. 2481 (1996).
- [6] N. Re, E. Gallo, C. Floriani, H. Miyasaka and N. Matsumoto, *Inorg. Chem.* **35**, 6004 (1996).
- [7] H. Miyasaka, N. Matsumoto, H. Okawa, N. Re, E. Gallo and C. Floriani, *J. Am. Chem. Soc.* **118**, 981 (1996).
- [8] P. J. McCarthy, R. J. Hovey, K. Ueno and A. E. Martell, *J. Am. Chem. Soc.* **77**, 5820 (1955).
- [9] P. Pfeifer, T. Hesse, H. Pfitzner, W. Scholl and H. Thielert, *J. Prakt. Chem.* **149**, 217 (1937).

- [10] N. Matsumoto, N. Takemoto, A. Ohyoshi and H. Okawa, *Bull. Chem. Soc. Jpn.* **61**, 2984 (1988).
- [11] G. M. Sheldrick, *SHELXT97 Program for the Refinement of Crystal Structure*, University of Göttingen, 1997.
- [12] H. Miyasaka, N. Matsumoto, N. Re, E. Gallo and C. Floriani, *Inorg. Chem.* **36**, 670 (1997).
- [13] H. Z. Kou, W. M. Bu, D. Z. Liao, Z. H. Jiang, S. P. Yan, Y. G. Fan and G. L. Wang, *J. Chem. Soc., Dalton Trans.* p. 4161 (1998).